



DATA SHEET

Alloy I74 (C17410) Strip

Materion Brush Performance Alloys' Alloy I74 strip is a mill hardened copper beryllium strip alloy designed for use in the Automotive, Appliance, and DataCom/TeleCom markets. It provides high yield and fatigue strength with high electrical conductivity and good resistance to stress relaxation. Typical applications include high reliability automotive terminals and spring contacts for switches and relays.

CHEMICAL COMPOSITION (weight percent)

Alloy	Beryllium	Cobalt	Copper
C17410	0.15-0.50	0.35-0.60	Balance

PHYSICAL PROPERTIES*

Elastic Modulus	Melting Point (Solidus)	Electrical Conductivity/resistivity	Density**	Thermal Expansion Coefficient	Thermal Conductivity (25 °C)
20,000 ksi 138 GPa	1880°F 1020 °C	45-60% IACS 2.9-3.8 μΩ-cm	0.318 lb/in ³ 8.80 g/cm ³	9.8x10 ⁻⁶ in/in °F 18.0x10 ⁻⁶ m/m °C	135 BTU/ft hr °F 230 W/ m K

*Properties specified for the precipitation age hardened (heat treated) condition

MECHANICAL PROPERTIES**

Temper**	0.2% Offset Yield Strength		Ultimate Tensile Strength		Elongation***	Hardness	Formability (Minimum Bend Radius to Thickness Ratio for a 90° Bend)****	
	ksi	MPa	ksi	MPa			Longitudinal	Transverse
½ HT (TH02)	80-100	550-690	95-115	665-790	10-20	180-230	0.5	0.5
HT (TH04)	100-120	690-825	110-130	760-895	7-17	210-278	1.2	5.0

**Properties may vary by thickness. Percent elongation numbers are valid for strip thicker than 0.004" (0.10 mm). Formability numbers valid for strip 0.010" (0.25 mm) and thinner.

Temper	10 ⁸ Cycle R=0 (Unidirectional) Fatigue Strength		10 ⁸ Cycle R=-1 (Fully Reversed) Fatigue Strength		1000 Hour Stress Relaxation Resistance*****		
	ksi	MPa	ksi	MPa	100°C	150°C	200°C
½ HT (TH02)	75-85	515-585	35-45	240-310	94%	82%	64%
HT (TH04)	85-95	585-655	55-65	380-450	95%	85%	77%

*****Stress remaining after 1000 hours exposure. Initial stress = 75% of the 0.2% offset yield strength

FORMS AVAILABLE


Alloy I74 mill hardened strip is available in widths ranging from 0.050" to 16" (1.27 mm to 452.7 mm) and in thicknesses ranging from 0.002" to 0.0787" (0.05 mm to 2.00 mm).

SPECIFICATIONS

C17410, ASTM B-768

RELATED INFORMATION

Additional information on Alloy I74 may be obtained by phoning 800-375-4205.

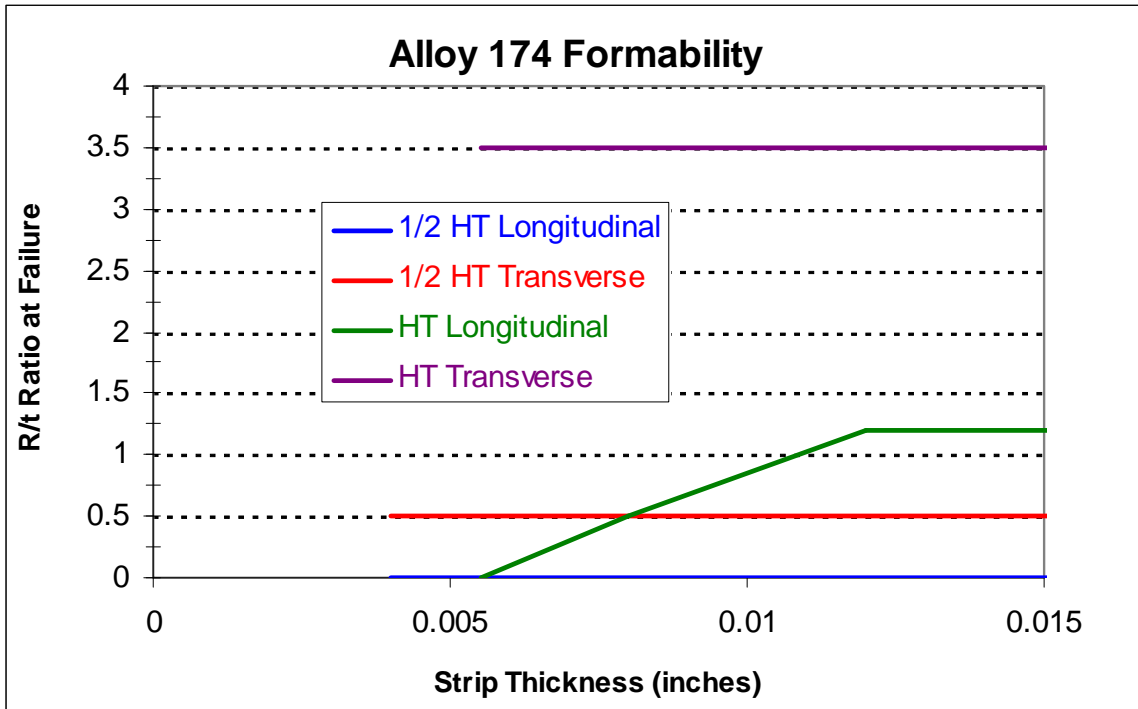

CHINA/HONG KONG
 TEL: + (852) 2318-1960 / 1907
brushalloysHK-info@materion.com

INDIA/PUNE
 TEL: + (91) 99606-33744
brushalloysIN-info@materion.com

SINGAPORE/ASEAN
 TEL: + (65) 6842-4456
brushalloysSG-info@materion.com

CHINA/SHANGHAI
 TEL: + (86) 21-5237-2328
brushalloysCN-info@materion.com

JAPAN
 TEL: + (81) 33 230 2961
brushalloysJP-info@materion.com

TAIWAN, R.O.C.
 TEL: + (886) 2-2747-8800 x-121
brushalloysTW-info@materion.com

GERMANY
 TEL: + (49) 711-830-930
brushalloysDE-info@materion.com

REPUBLIC OF KOREA
 TEL: + (82) 32-811-2171
brushalloysKR-info@materion.com

UNITED KINGDOM & IRELAND
 TEL: + (44) 118-930-3733
brushalloysUK-info@materion.com